

NOMENCLATURE

ρ	Density	κ_B	Boltzmann constant
ϕ	Volume fraction	T	Temperature
C_p	Heat capacity	Nu	Nusselt number
k	Conductivity	h	Convection coefficient
μ	Viscosity	L	Large
Ψ	Esfericity	Subscripts	
Re	Reynolds number	np	Nanoparticle
Pr	Prandtl number	bf	Base fluid
v	Mean velocity	eff	Effective
D	Diameter		

1. Introduction

Heat exchangers are widely used in many applications, for example, power production, refrigeration, chemical and food industry, etc. Actually, high prices of energy motivate industry to apply energy saving methods. For years, efforts performed to save energy include passive and active methods such as creating turbulence, extending the exchange surface or to use a fluid with higher thermophysical properties [1].

Recent advances in nanotechnology have allowed the development of a new category of liquids termed *nanofluids*, which was first used by Choi [2] to describe liquid suspensions containing nanometer-size particles (*nanoparticles*).

In recent years, experimental and numerical investigation about nanofluids and associate technology has increased, showing the notable concern in relation to save energy. Thus, this paper presents a review on convective heat transfer of nanofluids.

2. Preparation Methods for Nanofluids

2.1 Two-Step Method.

Two-step method is the most widely used for preparing nanofluids. Nanoparticles, nanofibers, nanotubes and other nanomaterials used in the Two-step method are first produced as dry powders by chemical or physical methods. Then, the nanomaterials (nanosized powder), will be dispersed into a base fluid with the help of ultrasonic agitation, magnetic force agitation, etc. Due to the high surface area and surface activity, nanoparticles have the tendency to aggregate. The use of surfactants is an important technique to enhance nanoparticles stability. However, its use under high temperature is also a big concern [3].

2.2 One-Step Method.

To reduce agglomeration of nanoparticles, has been developed a one-step physical vapor condensation method to prepare Cu/ethyleneglycol nanofluids [4]. The one step process consists in simultaneously making and dispersing the particles in the fluid. In this process, stages as drying, storage, transportation and dispersion of nanoparticles are avoided. Thus, the stability of

fluids is increased. The vacuum-SANSS (submerged arc nanoparticle synthesis system) is another one-step method to prepare nanofluids using dielectric liquids [5, 6].

One-step physical method can not synthesize nanofluids in large scale, and the cost is also high, so the one-step chemical method is developing rapidly. Zhu, et al. presented a novel one-step chemical method for preparing copper nanofluids by reducing $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$ with $\text{NaH}_2\text{PO}_2 \cdot \text{H}_2\text{O}$ in ethylene glycol under microwave irradiation. Well-dispersed and stabled suspended copper nanofluids were obtained [7]. Silver nanofluids (mineral oil-based) have been prepared using Zhu Method. Other important methods for nanofluids preparation were reviewed by Yu and Xie [3], as well as Stability Evaluation Methods as Sedimentation and Centrifugation Methods, Zeta Potential Analysis and Spectral Absorbency Analysis.

3. Properties of nanofluids

The most important properties of nanofluids are the thermophysical properties, in which specific heat, density, thermal conductivity and viscosity are very significant.

3.1 Effective density and specific heat.

Specific heat and effective density of nanofluids can be computed using classical equations derived for a two-phase mixture. Thus, the effective density of nanofluids is [8]:

$$\rho_{nf} = (1 - \phi)\rho_{bf} + \phi\rho_{np} \quad (1)$$

Specific heat of nanofluids is calculated using the next equation [9]:

$$C_{p\ nf} = \frac{(1-\phi)(\rho C_p)_{bf} + \phi(\rho C_p)_{np}}{(1-\phi)\rho_{bf} + \phi\rho_{np}} \quad (2)$$

The density and specific heat of the nanofluids are assumed to be a linear function of volume fraction due to lack of experimental data on their temperature dependence.

3.2 Thermal and effective thermal conductivity.

Keblinski et al. reported their idea on the possible mechanism of enhancing thermal conductivity, and suggested that the size effect, the clustering of nanoparticles and the surface adsorption could be the major reason of enhancement, while the Brownian motion of nanoparticles contributes much less than other factor [10]. Thermal conductivity and dynamic viscosity of the nanofluids are dependent not only the volume concentration of nanoparticle, but other parameters such as particle shape, size, slip mechanism, etc [1].

In the literature, the thermal enhancement ratio has been defined as the ratio of thermal conductivity of the nanofluid to the thermal conductivity of the base fluid (k_{eff}/k_{bf}). The effective thermal conductivity for a two-phase mixture k_{eff} is given by:

$$k_{eff} = \frac{2k_{np} + k_{bf} + \phi(k_{np} - k_{bf})}{2k_{np} + k_{bf} - \phi(k_{np} - k_{bf})} k_{bf} \quad (3)$$

Maxwell derived his model based on the assumption that the discontinuous phase is spherical in shape and the thermal conductivity of nanofluids depend on the thermal conductivity of spherical particles, the base fluid and the particle volume fraction [11].

Hamilton and Crosser [12] extended Maxwell work to cover none spherical particles and introduced the shape factor (n) which can be determined experimentally for different type of materials. The Hamilton and Crosser equation is given by:

$$k_{eff} = k_{bf} \left[\frac{k_{np} + (n-1)k_{bf} - (n-1)\phi(k_{bf} - k_{np})}{k_{np} + (n-1)k_{bf} + \phi(k_{bf} - k_{np})} \right] \quad (4)$$

where the empirical shape factor (n) is defined by $n = 3/\Psi$ in which Ψ is sphericity defined as the ratio of the surface areas of a sphere with the volume equal to that of the particle. The Hamilton-Crosser model reduces to Maxwell model when $\Psi = 1$.

Yu and Choi [14] modified Maxwell equation with the assumption that the base fluid molecules close to the solid surface of the NP form a solid-like layered structure. Hence the nanolayer works as a thermal bridge between the liquid base fluid and the solid nanoparticles, and this will enhance the effective thermal conductivity (thermal conductivity of nanolayer (k_{layer}) is higher than thermal conductivity of the liquid). The Yu-Choi model (for the case $k_{layer} = k_{np}$) is given by:

$$k_{eff} = \frac{k_{np} + 2k_{bf} + 2\phi(k_{np} - k_{bf})(1 + \beta)^3}{k_{np} + 2k_{bf} - \phi(k_{np} - k_{bf})(1 + \beta)^3} k_{bf} \quad (5)$$

where $\beta = \frac{h}{r}$ is the ratio between the nanolayer thickness (h) and the original particle ratio (r).

3.2.1 Theoretical models.

A summary of selective theoretical models on thermal conductivity of nanofluids are reported in Table 1. The dimensionless numbers for these models can be computed using the next equations:

Reynolds number:

$$Re = \frac{\rho v D}{\mu} \quad (6)$$

Prandtl number:

$$Pr = \frac{c_p \mu}{k} \quad (7)$$

Table 1. Theoretical models for effective thermal conductivity of nanofluids.

Reference	Year	Correlation	Details
Maxwell [11]	1881	$\frac{k_{eff}}{k_{bf}} = \frac{k_{np} + 2k_{bf} + 2\phi(k_{np} - k_{bf})}{k_{np} + 2k_{bf} - \phi(k_{np} - k_{bf})}$	Liquid and solid suspensions. Spherical particles.
Bruggemann [14]	1935	$\frac{k_{eff}}{k_{bf}} = \frac{1}{4} \left[(3\phi - 1) \frac{k_{np}}{k_{bf}} + (2 - 3\phi) \right] + \frac{k_{bf}}{4} \sqrt{\Delta}$ $\Delta = \left[(3\phi - 1)^2 \left(\frac{k_{np}}{k_{bf}} \right)^2 + (2 - 3\phi)^2 + 2(2 + 9\phi - 9\phi^2) \frac{k_{np}}{k_{bf}} \right]$	Spherical particles. Applicable to high concentration.
Hamilton and Crosser [12]	1962	$\frac{k_{eff}}{k_{bf}} = \frac{k_{np} + (n-1)k_{bf} - (n-1)\phi(k_{bf} - k_{np})}{k_{np} + (n-1)k_{bf} + \phi(k_{bf} - k_{np})}$	$n = 3/\Psi$ $\frac{k_{np}}{k_{bf}} > 100$
Yu and Choi [13]	2003	$\frac{k_{eff}}{k_{bf}} = \frac{k_{np} + 2k_{bf} + 2\phi(k_{np} - k_{bf})(1 + \beta)^3}{k_{np} + 2k_{bf} - \phi(k_{np} - k_{bf})(1 + \beta)^3}$	$k_{layer} = k_{np}$ $\beta = \frac{h}{r}$
Bhattacharya [15]	2004	$\frac{k_{eff}}{k_{bf}} = \frac{k_{np}}{k_{bf}} \phi + (1 - \phi)$ $k_{np} = \frac{1}{\kappa_B T^2 V} \sum_{j=0}^n (Q(0)Q(j\Delta T)) \Delta T$	Brownian dynamic
Prasher et. al [16]	2005	$\frac{k_{eff}}{k_{bf}} = (1 + ARe^m Pr^{0.333} \phi)Z$ $Z = \frac{k_{np} + 2k_{bf} + 2\phi(k_{np} - k_{bf})}{k_{np} + 2k_{bf} - \phi(k_{np} - k_{bf})}$	Effect of convection of the liquid near the particle included. A and m are constants. Nanospheres

Xue [17]	2005	$\frac{k_{eff}}{k_{bf}} = \frac{1 - \phi + 2\phi \frac{k_{np}}{k_{np} - k_{bf}} X}{1 - \phi + 2\phi \frac{k_{bf}}{k_{np} - k_{bf}} X}$ $X = \ln \frac{k_{np} + k_{bf}}{2k_{bf}}$	Nanospheres with interfacial shell.
----------	------	--	-------------------------------------

Published reports of thermal conductivity enhancement as a function of nanoparticle loading are summarized in Fig. 1 [18-27] and compared with theoretical models (Maxwell and Bruggemann). The most important results were obtained by Chon et al. and Wang et al. in which thermal conductivity enhancement is greater than 40 %.

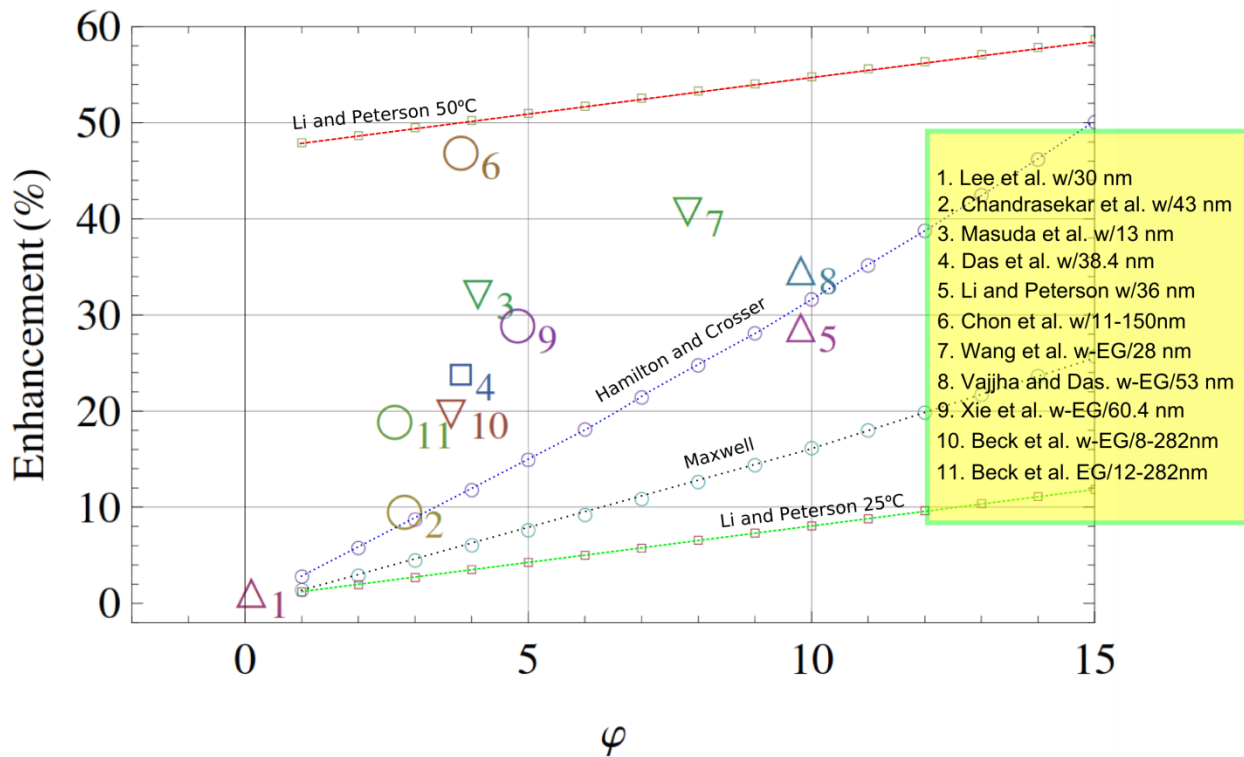


Figure 1. Thermal conductivity enhancement (%) as a function of the volume fraction of Al_2O_3 nanoparticles [18-27].

In the Fig. 1 we represented Li and Peterson model [16] which is an experimental correlation for Al₂O₃/water nanofluids. The Li and Peterson equation is given by:

$$\frac{k_{eff}-k_{bf}}{k_{bf}} = 0.764\phi + 0.0187(T - 273.15) - 0.462 \quad (8)$$

3.3 Viscosity and effective viscosity

Hypothetical analyses of the possible phenomena affecting the viscosity of nanofluids can be found in the literature, though they are very limited when compared with the depth of the theoretical models that can be found on thermal conductivity of nanofluids.

The Einstein's work [28] on infinitely diluted suspensions of uncharged hard spheres based on the vorticity of the particle shear field was the first theoretical work on viscosity of suspension.

The Einstein equation is given by:

$$\frac{\mu_{eff}}{\mu_{bf}} = (1 + [\eta]\phi) \quad (8)$$

where $[\eta]$ is the intrinsic viscosity of the suspension. This lineal equation is based on the assumed absence of interaction between the particles, and the coefficient $[\eta]$ is a function of shape of the particle, which for hard spheres was given as 2.5. The Einstein model is valid for solid volume concentration $\phi < 2.5\%$.

Contrary to the uncharged particle Einstein model, Smoluchowski [29] presented an effective viscosity model for charged particles in electrolyte suspension given by:

$$\frac{\mu_{eff}}{\mu_{bf}} = \left[1 + 2.5\phi \left\{ 1 + \frac{1}{K\mu_{bf}a^2} \left(\frac{\zeta D_E}{2\pi} \right)^2 \right\} \right] \quad (9)$$

where K is the specific conductivity of the electrolyte, a the radius of the solid particles, D_E the dielectric constant of the water and ζ the zeta potential of the particle with respect to the electrolytic medium.

Booth [30] in 1950 studied the overprediction made by Smoluchowski's model obtaining the next equation:

$$\frac{\mu_{eff}}{\mu_{bf}} = \left[1 + 2.5\phi \left\{ 1 + \sum_{l=1}^{\infty} b_l \left(\frac{e\zeta}{\kappa_B T} \right)^l \right\} \right] \quad (10)$$

in which b_l is the characteristic of electrolyte and e is the electronic charge on particles.

A summary of selective theoretical models on effective viscosity of nanofluids are reported in Table 2.

Table 2. Theoretical models on effective viscosity of nanofluids.

Reference	Year	Correlation	Details
Einstein [28]	1906	$\frac{\mu_{eff}}{\mu_{bf}} = 1 + 2.5\phi$	Infinitely diluted suspensions of spheres.
Hatchek [31]	1913	$\frac{\mu_{eff}}{\mu_{bf}} = 1 + 4.5\phi$	Applicable for up to 40% solid concentration.
Saito [32]	1950	$\frac{\mu_{eff}}{\mu_{bf}} = 1 + \frac{2.5}{(1 - \phi)} \phi$	Spherical rigid particles. Brownian motion. Very small and spherical particles.

Brinkman [33]	1952	$\frac{\mu_{eff}}{\mu_{bf}} = \frac{1}{(1 - \phi)^{2.5}}$	Spherical particles. Valid for highly moderated particle concentrations.
Lundgren [34]	1972	$\frac{\mu_{eff}}{\mu_{bf}} = \frac{1}{1 - 2.5\phi}$	Diluted concentration of spheres.
Batchelor [35]	1977	$\frac{\mu_{eff}}{\mu_{bf}} = 1 + 2.5\phi + 6.2\phi^2$	Spherical rigid particles. Brownian motion. Isotropic structure.
Thomas and Muthukmar [36]	1991	$\frac{\mu_{eff}}{\mu_{bf}} = 1 + 2.5\phi + 4.83\phi^2 + 6.4\phi^3$	Applicable for up to 40% solid concentration.

For Al₂O₃/water (Eq. 11) and Al₂O₃/ethylene glycol (Eq. 12) nanofluids Maiga et al. determined the effective viscosity as a function of nanoparticle volume fraction [37]:

$$\frac{\mu_{eff}}{\mu_{bf}} = 1 + 7.3\phi + 123\phi^2 \quad (11)$$

$$\frac{\mu_{eff}}{\mu_{bf}} = 1 - 0.19\phi + 306\phi^2 \quad (12)$$

Gabiela and Angel Humnic reviewed important models for effective viscosity determination as Wang, Tseng and Lin, Song, Buongiorno and other models [1].

3.4 Convective heat transfer

The enhancement of the heat transfer coefficient is a better signal than the thermal conductivity enhancement for nanofluids used in the design of heat exchange equipment.

Pak and Cho performed experiments on turbulent heat transfer using Al_2O_3 and TiO_2 /water nanofluids. The following model was obtained [9]:

$$Nu = 0.021Re^{0.8}Pr^{0.5} \quad (13)$$

In which $10^4 < Re < 10^5$, $6.5 < Pr < 12.3$ and $0 < \phi < 0.03$ (3 %vol).

The dimensionless Nu number is given by:

$$Nu = \frac{hD}{k}$$

Vajjha et al. [25] founded the next correlation (Eq. 14) for Al_2O_3 , CuO and SiO_2 /water nanofluids.

$$Nu = 0.065(Re^{0.65} - 60.22)(1 + 0.0169\phi^{0.15})Pr^{0.542} \quad (12)$$

In which $3000 < Re < 1.6 \cdot 10^4$ and $0 < \phi < 0.1$ (10 %vol).

For $\text{Al}_2\text{O}_3/\text{water}$ nanofluids Maiga obtained an important correlation [38, 39]. In Fig. 2 we represented Maiga [39] and Pak and Cho [9] models as a function of Pr and Re dimensionless number. The Maiga correlation results very important because the domain in which was obtained (Re and Pr) is applicable in the design of heat exchange equipment.

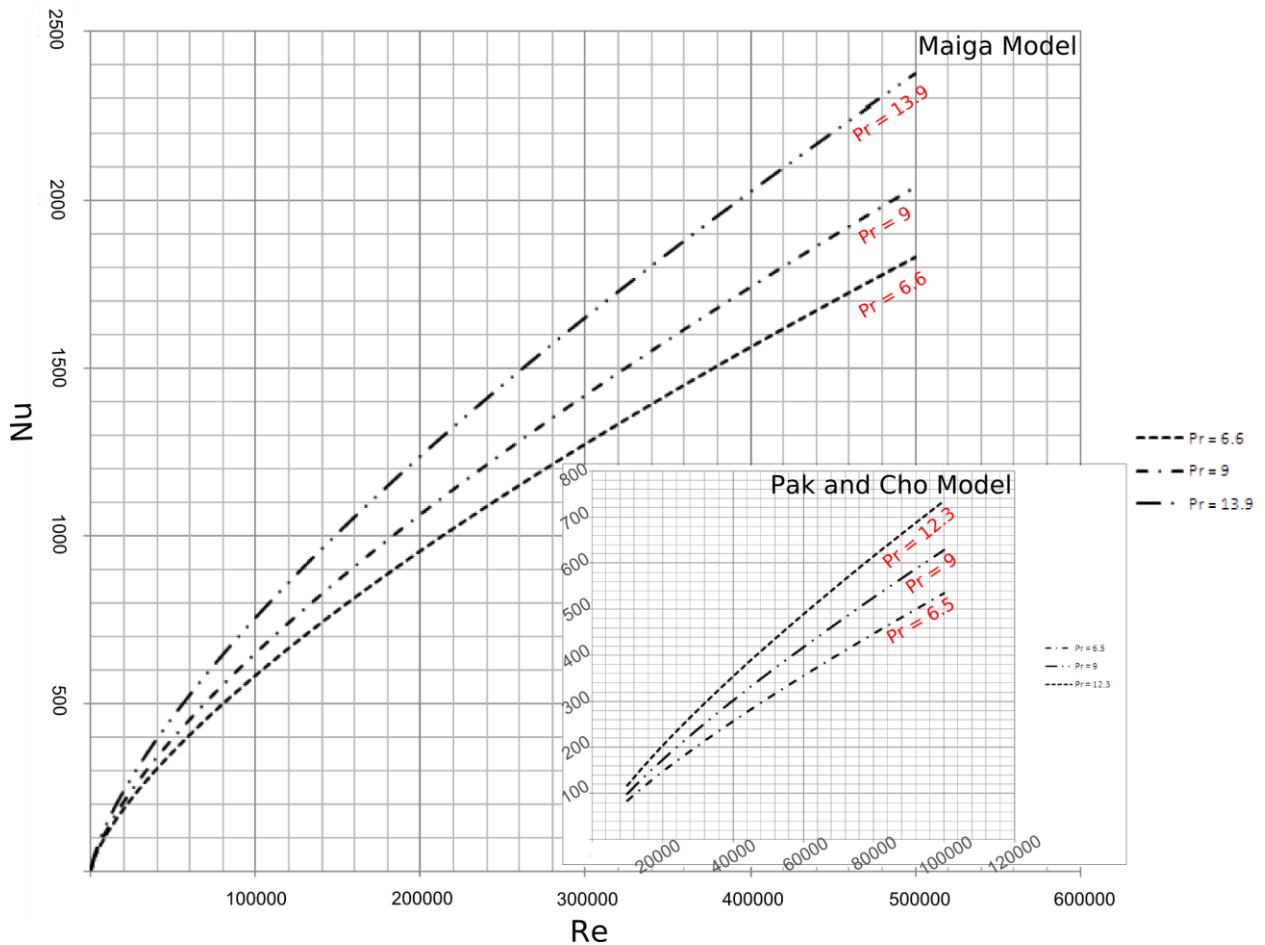


Figure 2. Maiga and Pak and Cho models. Maiga correlation [39] is valid for $0 < \phi < 0.1$ (10 % vol).

$\text{Al}_2\text{O}_3/\text{water}$ nanofluid convection coefficient is greater than water fluid. This fact allows designing heat exchanger equipment of less heat exchange area. Recent technological

developments, such as a microelectronic device are increasing thermal loads, requiring advances in cooling [40]. Other Nusselt correlations are listed in the next table (Table 3):

Table 3. Nusselt correlations for Al₂O₃/water, TiO₂/water, graphite-synthetic/oil, CuO/water and SiO₂/water nanofluids.

Reference	Year	Correlation	Details
Pak and Cho [9]	1998	$Nu = 0.021Re^{0.8}Pr^{0.5}$	Experimental study; turbulent flow. Al ₂ O ₃ /water nanofluids TiO ₂ /water nanofluids $0 < \phi < 0.03$ $10^4 < Re < 10^5$ $6.5 < Pr < 12.3$
Yang et al. [42]	2005	$Nu = aRe^bPr^{\frac{1}{3}}\left(\frac{D}{L}\right)^{\frac{1}{3}}\left(\frac{\mu_w}{\mu_b}\right)^{-0.14}$	Experimental study; laminar flow; graphite-synthetic/oil nanofluid. $0 < \phi < 0.02$ $5 < Re < 110$
Maiga [38]	2005	$Nu = 0.28Re^{0.35}Pr^{0.35}$ For constant temperature $Nu = 0.086Re^{0.55}Pr^{0.5}$ For constant wall heat flux	Numerical study; laminar flow; Al ₂ O ₃ /water nanofluids $0 < \phi < 0.1$ $Re \leq 1000$ $6.0 < Pr < 753$

Maiga [39]	2006	$Nu = 0.085Re^{0.71}Pr^{0.35}$	Numerical study; turbulent flow; Al ₂ O ₃ /water nanofluids $0 < \phi < 0.1$ $104 < Re < 5 \times 10^5$ $6.6 < Pr < 13.9$
Vijjha et al. [25]	2010	$Nu = 0.065(Re^{0.65} - 60.22)(1 + 0.0169\phi^{0.15})Pr^{0.542}$	Experimental study; turbulent flow. Al ₂ O ₃ /water nanofluids CuO/water nanofluids SiO ₂ /water nanofluids $0 < \phi < 0.06$ For CuO and SiO ₂ $0 < \phi < 0.1$ for Al ₂ O ₃ $3000 < Re < 1.6 \times 10^4$

3.5 Specific heat capacity of nanofluids

Specific heat of material is an important property to define thermal performance of any material. Generally, specific heat remains constant for liquid and solid materials at constant pressure and wide range of temperatures. In the nanofluid case may vary depending upon type of material, base fluids and volume fraction of nanoparticles. In the Pak and Cho [9] investigation with

Al_2O_3 /water nanofluids, they determined that 1.10-2.27% decrease in specific heat occurred for 1.34-2.78% volume fraction for nanoparticles size 13 nm. Zhou and Ni [42] determined that 47% maximum decrease in specific heat occurred for 21.7% volume fraction (Al_2O_3 /water nanofluids and nanoparticles size 45 nm). Shahrul et al. [43] concluded that for most of nanomaterials in base fluids, specific heat decreases with increase in volume fraction. However, in Sonawane et al. investigation [44], specific heat of Al_2O_3 /ATF nanofluids showed anomalous behavior of specific heat with volume fraction of nanoparticles. Experimental observations on various nanofluids showed increase in specific heat capacity [44-51]. Other investigations showed decrease in specific heat capacity of nanofluids [44,52,53].

4. Conclusions

The literature survey shows that nanofluids improve the heat transfer capability of conventional heat transfer fluids such as water by suspending nanoparticles in these base fluids. Important theoretical and experimental research on convective heat transfer show the significance of nanofluids to develop new technologies. Thus, this paper presents an overview of the recent investigation in the study of the thermophysical properties of nanofluids and their role in heat transfer enhancement. Theoretical and experimental correlation for the effective thermal conductivity, viscosity and Nusselt number of nanofluids are presented. Further studies are necessary to determine Nusselt number of nanofluids in more practical condition as jacked tanks, coils, etc.

5. Acknowledgements

The author thanks PhD. Miriam Palacios-Callender (West London University, UK) for her contribution to bibliography used in this paper.

6. References

1. Huminic G, Huminic A. Application of nanofluids in heat exchangers: a review. *Renewable and Sustainable Energy Reviews*. 2012 Oct 31;16(8):5625-38.
2. SU SC. Enhancing thermal conductivity of fluids with nanoparticles, developments and applications of non-Newtonian flows. *ASME FED*. 1995;105(99):231.
3. Yu W, Xie H. A review on nanofluids: preparation, stability mechanisms, and applications. *Journal of Nanomaterials*. 2012 Jan 1;2012:1.
4. Eastman JA, Choi SU, Li S, Yu W, Thompson LJ. Anomalously increased effective thermal conductivities of ethylene glycol-based nanofluids containing copper nanoparticles. *Applied physics letters*. 2001 Feb 5;78(6):718-20.
5. Lo CH, Tsung TT, Chen LC. Shape-controlled synthesis of Cu-based nanofluid using submerged arc nanoparticle synthesis system (SANSS). *Journal of Crystal Growth*. 2005 Apr 15;277(1):636-42.

6. Lo CH, Tsung TT, Chen LC, Su CH, Lin HM. Fabrication of copper oxide nanofluid using submerged arc nanoparticle synthesis system (SANSS). *Journal of Nanoparticle Research*. 2005 Jun 1;7(2):313-20.

7. Zhu HT, Lin YS, Yin YS. A novel one-step chemical method for preparation of copper nanofluids. *Journal of colloid and interface science*. 2004 Sep 1;277(1):100-3.

8. Xuan Y, Roetzel W. Conceptions for heat transfer correlation of nanofluids. *International Journal of heat and Mass transfer*. 2000 Oct 1;43(19):3701-7.

9. Pak BC, Cho YI. Hydrodynamic and heat transfer study of dispersed fluids with submicron metallic oxide particles. *Experimental Heat Transfer an International Journal*. 1998 Apr 1;11(2):151-70.

10. Keblinski P, Phillpot SR, Choi SU, Eastman JA. Mechanisms of heat flow in suspensions of nano-sized particles (nanofluids). *International journal of heat and mass transfer*. 2002 Feb 28;45(4):855-63.

*11. J.C. Maxwell, *Treatise on Electricity and Magnetism*, Oxford University Press, London, 1904.

*12. Han ZH, Cao FY, Yang B. Synthesis and thermal characterization of phase-changeable indium/polyalphaolefin nanofluids. *Applied Physics Letters*. 2008 Jun 16;92(24):243104.

13. Hamilton RL, Crosser OK. Thermal conductivity of heterogeneous two-component systems. *Industrial & Engineering chemistry fundamentals*. 1962 Aug;1(3):187-91.

14. Yu W, Choi SU. The role of interfacial layers in the enhanced thermal conductivity of nanofluids: a renovated Maxwell model. *Journal of Nanoparticle Research*. 2003 Apr 1;5(1-2):167-71.

15. Bruggeman VD. Berechnung verschiedener physikalischer Konstanten von heterogenen Substanzen. I. Dielektrizitätskonstanten und Leitfähigkeiten der Mischkörper aus isotropen Substanzen. *Annalen der physik*. 1935 Jan 1;416(7):636-64.

16. Bhattacharya PS, Saha SK, Yadav A, Phelan PE, Prasher RS. Brownian dynamics simulation to determine the effective thermal conductivity of nanofluids. *Journal of Applied Physics*. 2004 Jun 1;95(11):6492-4.

17. Prasher R, Bhattacharya P, Phelan PE. Thermal conductivity of nanoscale colloidal solutions (nanofluids). *Physical review letters*. 2005 Jan 18;94(2):025901.

18. Xue QZ. Model for thermal conductivity of carbon nanotube-based composites. *Physica B: Condensed Matter*. 2005 Nov 1;368(1):302-7.

19. Lee JH, Hwang KS, Jang SP, Lee BH, Kim JH, Choi SU, Choi CJ. Effective viscosities and thermal conductivities of aqueous nanofluids containing low volume concentrations of Al₂O₃ nanoparticles. *International Journal of Heat and Mass Transfer*. 2008 Jun 30;51(11):2651-6.

20. Chandrasekar M, Suresh S, Senthilkumar T. Mechanisms proposed through experimental investigations on thermophysical properties and forced convective heat transfer characteristics of various nanofluids—a review. *Renewable and Sustainable Energy Reviews*. 2012 Aug 31;16(6):3917-38.

21. Masuda H, Ebata A, Teramae K. Alteration of thermal conductivity and viscosity of liquid by dispersing ultra-fine particles. Dispersion of Al₂O₃, SiO₂ and TiO₂ ultra-fine particles

22. Das SK, Putra N, Thiesen P, Roetzel W. Temperature dependence of thermal conductivity enhancement for nanofluids. *Journal of heat transfer*. 2003 Aug 1;125(4):567-74.

23. Li CH, Peterson GP. Experimental investigation of temperature and volume fraction variations on the effective thermal conductivity of nanoparticle suspensions (nanofluids). *Journal of Applied Physics*. 2006 Apr 15;99(8):084314.
24. Chon CH, Kihm KD, Lee SP, Choi SU. Empirical correlation finding the role of temperature and particle size for nanofluid (Al₂O₃) thermal conductivity enhancement. *Applied Physics Letters*. 2005 Oct 10;87(15):153107.
25. Wang X, Xu X, Choi SU. Thermal conductivity of nanoparticle-fluid mixture. *Journal of thermophysics and heat transfer*. 1999 Oct 1;13(4):474-80.
26. Vajjha RS, Das DK. Experimental determination of thermal conductivity of three nanofluids and development of new correlations. *International Journal of Heat and Mass Transfer*. 2009 Oct 31;52(21):4675-82.
27. Xie H, Wang J, Xi T, Liu Y, Ai F. Dependence of the thermal conductivity of nanoparticle-fluid mixture on the base fluid. *Journal of Materials Science Letters*. 2002 Oct 1;21(19):1469-71.
28. Beck MP, Yuan Y, Warriar P, Teja AS. The effect of particle size on the thermal conductivity of alumina nanofluids. *Journal of Nanoparticle Research*. 2009 Jul 1;11(5):1129-36.

29. Einstein A, Beck A, Havas P. The collected papers of Albert Einstein. Princeton University Press; 1989.

30. Smoluchowski MV. Theoretische bemerkungen über die viskosität der kolloide. Kolloid-Zeitschrift. 1916 May 1;18(5):190-5.

31. Booth F. The electroviscous effect for suspensions of solid spherical particles. In Proceedings of the Royal Society of London A: Mathematical, Physical and Engineering Sciences 1950 Oct 24 (Vol. 203, No. 1075, pp. 533-551). The Royal Society.

32. Hatschek E. The general theory of viscosity of two-phase systems. Transactions of the Faraday Society. 1913;9:80-92.

33. Saitô N. Concentration dependence of the viscosity of high polymer solutions. I. Journal of the Physical Society of Japan. 1950;5(1):4-8.

34. Brinkman HC. The viscosity of concentrated suspensions and solutions. The Journal of Chemical Physics. 1952 Apr;20(4):571-.

35. Lundgren TS. Slow flow through stationary random beds and suspensions of spheres. *Journal of Fluid Mechanics*. 1972 Jan;51(2):273-99.

36. Batchelor GK. The effect of Brownian motion on the bulk stress in a suspension of spherical particles. *Journal of fluid mechanics*. 1977 Nov;83(1):97-117.

37. Thomas CU, Muthukumar M. Three-body hydrodynamic effects on viscosity of suspensions of spheres. *The Journal of chemical physics*. 1991 Apr 1;94(7):5180-9.

38. Maïga SE, Nguyen CT, Galanis N, Roy G. Heat transfer behaviours of nanofluids in a uniformly heated tube. *Superlattices and Microstructures*. 2004 Jun 30;35(3):543-57.

39. Maiga SE, Palm SJ, Nguyen CT, Roy G, Galanis N. Heat transfer enhancement by using nanofluids in forced convection flows. *International journal of heat and fluid flow*. 2005 Aug 31;26(4):530-46.

40. El Bécaye Maïga S, Tam Nguyen C, Galanis N, Roy G, Maré T, Coqueux M. Heat transfer enhancement in turbulent tube flow using Al₂O₃ nanoparticle suspension. *International Journal of Numerical Methods for Heat & Fluid Flow*. 2006 Apr 1;16(3):275-92.
41. Keblinski P, Eastman JA, Cahill DG. Nanofluids for thermal transport. *Materials today*. 2005 Jun 30;8(6):36-44.
42. Yang Y, Zhang ZG, Grulke EA, Anderson WB, Wu G. Heat transfer properties of nanoparticle-in-fluid dispersions (nanofluids) in laminar flow. *International Journal of Heat and Mass Transfer*. 2005 Mar 31;48(6):1107-16.
43. Zhou SQ, Ni R. Measurement of the specific heat capacity of water-based Al₂O₃ nanofluid. *Applied Physics Letters*. 2008 Mar 3;92(9):093123.
44. Shahrul IM, Mahbubul IM, Khaleduzzaman SS, Saidur R, Sabri MF. A comparative review on the specific heat of nanofluids for energy perspective. *Renewable and Sustainable Energy Reviews*. 2014 Oct 31;38:88-98.

45. Sonawane S, Patankar K, Fogla A, Puranik B, Bhandarkar U, Kumar SS. An experimental investigation of thermo-physical properties and heat transfer performance of Al₂O₃-aviation turbine fuel nanofluids. *Applied Thermal Engineering*. 2011 Oct 31;31(14):2841-9.
46. Starace AK, Gomez JC, Wang J, Pradhan S, Glatzmaier GC. Nanofluid heat capacities. *Journal of Applied Physics*. 2011 Dec 15;110(12):124323.
47. Shin D, Banerjee D. Specific heat of nanofluids synthesized by dispersing alumina nanoparticles in alkali salt eutectic. *International Journal of Heat and Mass Transfer*. 2014 Jul 31;74:210-4.
48. Mohebbi A. Prediction of specific heat and thermal conductivity of nanofluids by a combined equilibrium and non-equilibrium molecular dynamics simulation. *Journal of Molecular Liquids*. 2012 Nov 30;175:51-8.
49. Murshed SS, De Castro CN. Superior thermal features of carbon nanotubes-based nanofluids—A review. *Renewable and Sustainable Energy Reviews*. 2014 Sep 30;37:155-67.
50. Nelson IC, Banerjee D, Ponnappan R. Flow loop experiments using polyalphaolefin nanofluids. *Journal of thermophysics and heat transfer*. 2009 Oct 1;23(4):752.

51. Akhavan-Behabadi MA, Pakdaman MF, Ghazvini M. Experimental investigation on the convective heat transfer of nanofluid flow inside vertical helically coiled tubes under uniform wall temperature condition. *International Communications in Heat and Mass Transfer*. 2012 Apr 30;39(4):556-64.

52. Ho MX, Pan C. Optimal concentration of alumina nanoparticles in molten Hitec salt to maximize its specific heat capacity. *International Journal of Heat and Mass Transfer*. 2014 Mar 31;70:174-84.

53. Ho MX, Pan C. Optimal concentration of alumina nanoparticles in molten Hitec salt to maximize its specific heat capacity. *International Journal of Heat and Mass Transfer*. 2014 Mar 31;70:174-84.

54. Chandrasekar M, Suresh S, Senthilkumar T. Mechanisms proposed through experimental investigations on thermophysical properties and forced convective heat transfer characteristics of various nanofluids—a review. *Renewable and Sustainable Energy Reviews*. 2012 Aug 31;16(6):3917-38.

55. He Q, Wang S, Tong M, Liu Y. Experimental study on thermophysical properties of nanofluids as phase-change material (PCM) in low temperature cool storage. *Energy conversion and management*. 2012 Dec 31;64:199-205.